



# Standard Classification System for Rubber Products in Automotive Applications<sup>1</sup>

This standard is issued under the fixed designation D 2000; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

*This specification has been approved for use by agencies of the Department of Defense.*

## 1. Scope

1.1 This classification system tabulates the properties of vulcanized rubber materials (natural rubber, reclaimed rubber, synthetic rubbers, alone or in combination) that are intended for, but not limited to, use in rubber products for automotive applications.

NOTE 1—This classification system may serve many of the needs of other industries in much the same manner as SAE numbered steels. It must be remembered, however, that this system is subject to revision when required by automotive needs. It is recommended that the latest revision always be used.

1.2 This classification system is based on the premise that the properties of all rubber products can be arranged into characteristic material designations. These designations are determined by *types*, based on resistance to heat aging, and *classes*, based on resistance to swelling in oil. Basic levels are thus established which, together with values describing additional requirements, permit complete description of the quality of all elastomeric materials.

1.3 In all cases where the provisions of this classification system would conflict with those of the detailed specifications for a particular product, the latter shall take precedence.

NOTE 2—When the rubber product is to be used for purposes where the requirements are too specific to be completely prescribed by this classification system, it is necessary for the purchaser to consult the supplier in advance, to establish the appropriate properties, test methods, and specification test limits.

1.4 The values stated in SI units are to be regarded as the standard.

## 2. Referenced Documents

### 2.1 ASTM Standards:

D 395 Test Methods for Rubber Property—Compression Set<sup>2</sup>

D 412 Test Methods for Vulcanized Rubber and Thermoplastic Rubbers and Thermoplastic Elastomers—Tension<sup>2</sup>

D 429 Test Methods for Rubber Property—Adhesion to Rigid Substrates<sup>2</sup>

D 430 Test Methods for Rubber Deterioration—Dynamic Fatigue<sup>2</sup>

D 471 Test Method for Rubber Property—Effect of Liquids<sup>2</sup>

D 573 Test Method for Rubber—Deterioration in an Air Oven<sup>2</sup>

D 575 Test Methods for Rubber Properties in Compression<sup>2</sup>

D 624 Test Method for Tear Strength of Conventional Vulcanized Rubber and Thermoplastic Elastomers<sup>2</sup>

D 865 Test Method for Rubber—Deterioration by Heating in Air (Test Tube Enclosure)<sup>2</sup>

D 925 Test Methods for Rubber Property—Staining of Surfaces (Contact, Migration, and Diffusion)<sup>2</sup>

D 945 Test Methods for Rubber Properties in Compression or Shear (Mechanical Oscillograph)<sup>2</sup>

D 1053 Test Methods for Rubber Property—Stiffening at Low Temperatures: Flexible Polymers and Coated Fabrics<sup>2</sup>

D 1171 Test Method for Rubber Deterioration—Surface Ozone Cracking Outdoors or Chamber (Triangular Specimens)<sup>2</sup>

D 1329 Test Method for Evaluating Rubber Property—Retraction at Lower Temperatures (TR Test)<sup>2</sup>

D 1349 Practice for Rubber—Standard Temperatures for Testing<sup>2</sup>

D 1418 Practice for Rubber and Rubber Latices—Nomenclature<sup>2</sup>

D 2137 Test Methods for Rubber Property—Brittleness Point of Flexible Polymers and Coated Fabrics<sup>2</sup>

D 2240 Test Method for Rubber Property—Durometer Hardness<sup>2</sup>

D 3183 Practice for Rubber—Preparation of Pieces for Test Purposes from Products<sup>2</sup>

D 5964 Practice for Rubber—IRM 902 and IRM 903 Replacement Oils for ASTM No. 2 and ASTM No. 3 Oils<sup>2</sup>

## 3. Purpose

3.1 The purpose of this classification system is to provide guidance to the engineer in the selection of practical, commercially available rubber materials, and further to provide a method for specifying these materials by the use of a simple

<sup>1</sup> This classification system is under the jurisdiction of ASTM Committee D11 on Rubber and is the direct responsibility of Subcommittee D11.30 on Classification of Rubber Compounds.

Current edition approved July 10, 2001. Published September 2001. Originally published as D 2000 – 62 T. Last previous edition D 2000 – 00.

<sup>2</sup> *Annual Book of ASTM Standards*, Vol 09.01.

“line call-out” designation.

3.2 This classification system was developed to permit the addition of descriptive values for future rubber materials without complete reorganization of the classification system and to facilitate the incorporation of future new test methods to keep pace with changing industry requirements.

**4. Type and Class**

4.1 The prefix letter “M” shall be used to indicate that the classification system is based on SI units.

NOTE 3—Call outs not prefixed by the letter M refer to an earlier classification system based on inch-pound units. This was published in editions up to 1980.

4.2 Rubber materials shall be designated on the basis of *type* (heat resistance) and *class* (oil resistance). Type and class are indicated by letter designations as shown in Table 1 and Table 2 and illustrated in 9.1.

4.3 *Type* is based on changes in tensile strength of not more than ±30 %, elongation of not more than – 50 %, and hardness of not more than ±15 points after heat aging for 70 h at an appropriate temperature. The temperatures at which these materials shall be tested for determining type are listed in Table 1.

4.4 *Class* is based on the resistance of the material to swelling in ASTM Oil No. 3 after 70-h immersion at a temperature determined from Table 1, except that a maximum temperature of 150°C (the upper limit of oil stability) shall be used. Limits of swelling for each class are shown in Table 2.

4.4.1 ASTM No. 2 and No. 3 Oils have been replaced by IRM 902 and 903 Oils, respectively, under Practice D 5964. These Oils are similar but not identical to ASTM No. 2 and No. 3 Oils.

4.4.2 Substitutability of IRM 902 and 903 Oils for ASTM No. 2 and No. 3 Oils has not been established, as their swelling characteristics are different and may affect compound classification.

NOTE 4—The selection of type based on heat resistance is understood to be indicative of the inherent heat resistance that can be normally expected from commercial compositions. Likewise, choice of class is based on the range of volume swell normally expected from such commercial compositions as established by type. *The fact that a type and class of material is listed in Table 6, under Basic Requirements, indicates that materials that meet these requirements for heat and oil resistance are commercially available.*

4.5 The letter designations shall always be followed by a three-digit number to specify the hardness and the tensile

**TABLE 2 Basic Requirements for Establishing Class by Volume Swell**

Class	Volume Swell, max, %
A	no requirement
B	140
C	120
D	100
E	80
F	60
G	40
H	30
J	20
K	10

**TABLE 3 Meaning of Suffix Letters**

Suffix Letter	Test Required
A	Heat Resistance
B	Compression Set
C	Ozone or Weather Resistance
D	Compression-Deflection Resistance
EA	Fluid Resistance (Aqueous)
EF	Fluid Resistance (Fuels)
EO	Fluid Resistance (Oils and Lubricants)
F	Low-Temperature Resistance
G	Tear Resistance
H	Flex Resistance
J	Abrasion Resistance
K	Adhesion
M	Flammability Resistance
N	Impact Resistance
P	Staining Resistance
R	Resilience
Z	Any special requirement, which shall be specified in detail

**TABLE 4 Suffix Numbers to Indicate Temperature of Test**

Applicable Suffix Requirements	Second Suffix Number	Test Temperature, °C <sup>A</sup>
A, B, C, EA, EF, EO, G, K	11	275
	10	250
	9	225
	8	200
	7	175
	6	150
	5	125
	4	100
	3	70
	2	38
	1	23
	0	<sup>B</sup>
F	1	23
	2	0
	3	-10
	4	-18
	5	-25
	6	-35
	7	-40
	8	-50
	9	-55
	10	-65
	11	-75
	12	-80

<sup>A</sup> These test temperatures are based on Practice D 1349.

<sup>B</sup> Ambient temperature in the case of outdoor testing.

**TABLE 1 Basic Requirements for Establishing Type by Temperature**

Type	Test Temperature, °C
A	70
B	100
C	125
D	150
E	175
F	200
G	225
H	250
J	275
K	300

strength—for example, 505. The first digit indicates durometer hardness, Type A, for example, 5 for 50 ± 5, 6 for 60 ± 5. The next two digits indicate the minimum tensile strength—for example, 05 for 5 MPa, 14 for 14 MPa. *Correlation of*

available materials for desired hardness and tensile strength is obtained through the elongation values in Table 6. See 7.2.

**5. Grade Numbers, Suffix Letters, and Number**

5.1 *Grade Numbers*—Since the basic requirements do not always describe sufficiently all the necessary qualities, provision is made for deviation or adding requirements through a system of prefix grade numbers. Grade No. 1 indicates that only the basic requirements are compulsory, and no suffix requirements are permitted. Grades other than No. 1 are used for expressing deviation or additional requirements and are listed as “Available Suffix Grade Numbers” in the last column under Basic Requirements in Table 6. A grade number is written as a material prefix number preceding the letters for type and class (see 9.1). Grade No. 1 is always an available suffix grade number, and thus is not referenced in the last column of each basic requirement table.

5.2 *Suffix Letters*—The suffix letters that may be used, together with their meaning, appear in Table 3.

5.3 *Suffix Numbers*—Each suffix letter should preferably be followed by two suffix numbers (see Note 6 in 8.1). *The first suffix number always indicates the test method; time of test is part of the method and is taken from the listings in Table 5. The second suffix number, if used, always indicates the temperature of test and is taken from Table 4.* Where three-digit numbers are required, they are separated by a dash—for example: –10; B4–10; F1–11.

**6. Composition and Manufacture**

6.1 This classification system is predicated upon materials furnished under a specification based thereon being manufactured from natural rubber, reclaimed rubber, synthetic rubber, alone or in combination, together with added compounding ingredients of such nature and quantity as to produce vulcanizates that comply with the specified requirements. All materials and workmanship shall be in accordance with good commercial practice, and the resulting product shall be free of porous areas, weak sections, bubbles, foreign matter, or other defects affecting serviceability.

6.2 *Color*—With the exception of FC, FE, FK, and GE materials, the values in the material tables are based on black compounds and comparable values may not be available in color.

**7. Basic Requirements**

7.1 The basic requirements for physical properties specified

in Table 6<sup>3</sup> are based on values obtained from standard laboratory test specimens prepared and tested in accordance with the applicable ASTM test methods. *Test results from specimens prepared from finished products may not duplicate values obtained from standard test specimens.*

NOTE 5—When standard test specimens are cut from finished parts in accordance with Practice D 3183, a deviation to the extent of 10 % (on tensile strength and elongation values only) is permissible when agreed upon by the purchaser and the supplier. This deviation is permissible *only* because of the recognized effects of knitting, grain, and buffing on the material when test specimens are prepared from finished parts and tested for tensile strength and elongation. When differences due to the method of processing or to the difficulty in obtaining suitable test specimens from the finished part arise, the purchaser and the supplier may agree on acceptable deviations. This can be done by comparing results of standard test specimens with those obtained on actual parts.

7.2 The available materials are listed in the appropriate material section of the table, giving each hardness and tensile strength with its appropriate elongation value. Also, there is a repetition of the values for the basic heat and oil aging requirements for the material resulting from the assignment of type and class. In addition, values for compression set, normally a basic requirement to ensure proper vulcanization, are specified.

**8. Suffix Requirements**

8.1 Suffix requirements shall be specified *only as needed* to define qualities necessary to meet service requirements. These suffix requirements are set forth for the various grade numbers. Suffix letters and suffix numbers describing these suffix requirements may be used singly or in combination, *but not all suffix values available for a given material need be specified.*

NOTE 6—Examples of the use of suffix letters and numbers would be A14 and EO34. Suffix A (Table 3) stands for heat resistance, Suffix 1 (Table 5) specifies that the test be run in accordance with Test Method D 573 for 70 h, and Suffix A (Table 4) indicates the temperature of test as 100°C. Similarly, Suffix EO34 indicates resistance in ASTM Oil No. 3 in accordance with Test Method D 471 for 70 h at 100°C.<sup>4</sup>

8.2 Basic requirements are always in effect, unless superseded by specific suffix requirements in the “line call-out.”

<sup>3</sup> Tensile values are shown as pounds per square inch in Table 6 for information only.

<sup>4</sup> ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

**TABLE 5 ASTM Test Methods**

Basic Requirements and First Suffix No.	Basic	1	2	3	4	5	6	7	8	9
		Requirement or Suffix Letter								
Tensile Strength, Elongation	D 412, die C	...	...	...	...	...	...	...	...	...
Durometer Hardness, Type A	D 2240	...	...	...	...	...	...	...	...	...
Suffix A, Heat Resistance	...	D 573, 70 h	D 865, 70 h	D 865, 168 h	D 573, 168 h	D 573, 1000 h	D 865, 1000 h	...	...	...

TABLE 5 Continued

Basic Requirements and First Suffix No.	Basic	1	2	3	4	5	6	7	8	9
Suffix B, Compression Set, Standard Test Specimen Cut from a Slab	...	D 395, 22 h, Method B, solid	D 395, 70 h, Method B, solid	D 395, 22 h, Method B, plied	D 395, 70 h, Method B, plied	D 395, 1000 h, Method B, solid	D 395, 1000 h, Method B, plied	...	...	...
Suffix C, Ozone or Weather Resistance	...	D 1171, ozone <sup>A</sup> exposure, Method A	D 1171, <sup>B</sup> weather	D 1171, ozone <sup>C</sup> exposure, Method B	...	...	...	...	...	...
Suffix D, Compression-Deflection Resistance	...	D 575, Method A	D 575, Method B	...	...	...	...	...	...	...
Suffix EO, Oil Resistance	...	D 471, ASTM Oil No. 1, <sup>D</sup> 70 h	D 471, ASTM Oil No. 2, <sup>D</sup> 70 h	D 471, ASTM Oil No. 3, <sup>D</sup> 70 h	D 471, ASTM Oil No. 1, 168 h	D 471, ASTM Oil No. 2, 168 h	D 471, ASTM Oil No. 3, 168 h	D 471, Service Liquid No. 101, 70 h	D 471, Oil as specifically designated in Table 6, 70 h	...
Suffix EF, Fluid Resistance	...	D 471, Reference Fuel A, 70 h	D 471, Reference Fuel B, 70 h	D 471, Reference Fuel C, 70 h	D 471, Reference Fuel D, 70 h	D 471, Volume Percent Reference Fuel D Plus 15 Volume Percent Denatured Ethanol, 70 h	...	...	...	...
Suffix EA, Aqueous Fluid Resistance	...	D 471, Distilled Water, 70 h <sup>E</sup>	D 471, Equal Parts by Volume Distilled Water-Reagent Grade Ethylene Glycol, 70 h <sup>F</sup>	...	...	...	...	...	...	...
Suffix F, Low-Temperature Resistance	...	D 2137, Method A, 9.3.2, 3 min	D 1053, 5 min, T <sub>2</sub> , T <sub>5</sub> , T <sub>10</sub> , T <sub>50</sub> , or T <sub>100</sub>	D 2137, Method A 9.3.2, 22 h	D 1329, 38.1 mm die, 50 % elongation, retraction 10 % min	D 1329, 38.1 mm die, 50 % elongation, retraction 50 % min	...	...	...	...
Suffix G, Tear Resistance	...	D 624, die B	D 624, die C	...	...	...	...	...	...	...
Suffix H, Flex Resistance	...	D 430, Method A	D 430, Method B	D 430, Method C	...	...	...	...	...	...
Suffix J, Abrasion Resistance	...	D 430, Method A <sup>G</sup>	...	...	...	...	...	...	...	...
Suffix K, Adhesion	...	D 429, Method A	D 429, Method B	Bond made after vulcanization	...	...	...	...	...	...
Suffix M, Flammability Resistance <sup>G</sup>	...	...	...	...	...	...	...	...	...	...
Suffix N, Impact Resistance <sup>G</sup>	...	...	...	...	...	...	...	...	...	...
Suffix P, Staining Resistance	...	D 925, Method A	D 925, Method B Control Panel	...	...	...	...	...	...	...
Suffix R, Resilience	...	D 945	...	...	...	...	...	...	...	...
Suffix Z, Special Requirement <sup>G</sup>	...	...	...	...	...	...	...	...	...	...

<sup>A</sup> Use ozone chamber exposure method of Test Method D 1171, Method A.

<sup>B</sup> Test Method D 1171, Weather Test, is 6 weeks duration. Test area and time of year to be agreed upon by the purchaser and the manufacturer

<sup>C</sup> Use ozone chamber exposure method of Test Method D 1171, Method B.

<sup>D</sup> ASTM No. 2 and No. 3 Oils are no longer commercially available. They have been replaced by IRM 902 and 903 Oils, respectively. See 4.4.1. ASTM Oil No. 1, IRM 902 and IRM 903 may be ordered from Penreco, 4426 East Washington Blvd., Los Angeles, CA 90023-4476. They are also distributed by R. E. Carroll, Inc., P.O. Box 5806, Trenton, NJ 08638-0806.

<sup>E</sup> Distilled water shall be used. Volume increase by water displacement method, except alcohol dip omitted. When determining changes in tensile strength, elongation, and hardness, test tube to be ¾ full after specimens are immersed. Determination to be made after 30 min. Cool in distilled water, acetone dip to be omitted.


<sup>F</sup> Equal parts by volume of distilled water and reagent grade ethylene glycol. Volume increase by displacement method, except alcohol dip omitted. When determining changes in tensile strength, elongation, and hardness, test tube to be ¾ full after specimens are immersed. Determination to be made after 30 min. Cool in distilled water, acetone dip to be omitted.

<sup>G</sup> Test method to be specified.

**9. Line Call-Outs**

9.1 A “line call-out,” which is a specification, shall contain: the documents names, the prefix letter M, the grade number, the material designation (type and class), and the hardness and tensile strength, followed by the appropriate suffix requirements. Following is an example of a “line call-out” or specification:

*ASTM D 2000 M2BC 507 A14EO34*

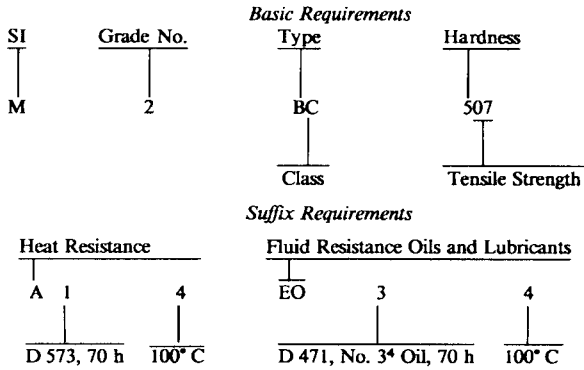

In this example, basic requirements for heat resistance and fluid resistance are superseded by suffix requirements. However, the basic requirement of 80 % for compression set, which is not included as a suffix requirement, is not superseded and therefore shall be met as specified in Table 6.

**10. Test Methods**

10.1 The applicable test methods are listed in Table 5.

**11. Sampling and Inspection**

11.1 A lot, unless otherwise specified, shall consist of all products of the same material submitted for inspection at the same time.

11.2 When proof of conformance with a specification based on this classification system is required, the supplier shall, upon request of the purchaser at the time of ordering, furnish a sufficient number of samples to permit the performance of the required tests. Test specimens shall be prepared as prescribed in 7.1. The samples shall be warranted to have equivalent cure and to be from the same run or batch of compound used in the lot.

**TABLE 6 Basic and Supplementary (Suffix) Requirements for Classification of Elastomeric Materials**

Basic Requirements							AA MATERIALS
Durometer Hardness, $\pm 5$ Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 70°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 70C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 70°C	Available Suffix Grade Numbers
	MPa	psi					
30	7	1015	400				2, 4
30	10	1450	400				2, 4
30	14	2031	400				2, 4
40	7	1015	400				2, 4
40	10	1450	400				2, 4
40	14	2031	400				2, 4
40	17	2466	500				2, 4
40	21	3046	600				2, 4
50	3	435	250				2
50	6	870	250				2
50	7	1015	400				2, 3
50	8	1160	400				2, 3
50	10	1450	400				2, 3, 4, 5
50	14	2031	400				2, 3, 4, 5
50	17	2466	400				2, 3, 4, 5
50	21	3046	500				2, 3, 4, 5
60	3	435	250				2
60	6	870	250				2
60	7	1015	300	Change in tensile strength, $\pm 30$ % Change in ultimate elongation, $- 50$ % max Change in durometer hardness, $\pm 15$ points	No Requirement	Compression set, 50 % max	2, 3
60	8	1160	300				2, 3
60	10	1450	350				2, 3, 4, 5
60	14	2031	400				2, 3, 4, 5
60	17	2466	400				2, 3, 4, 5
60	21	3046	400				2, 3, 4, 5
60	24	3481	500				2, 3, 4, 5
70	3	435	150				
70	6	870	150			2	
70	7	1015	200			2, 3	
70	8	1160	200			2, 3	
70	10	1450	250			2, 3, 4, 5	
70	14	2031	300			2, 3, 4, 5	
70	17	2466	300			2, 3, 4, 5	
70	21	3046	350			2, 3, 4, 5	
80	3	435	100			2	
80	7	1015	100			2	
80	10	1450	150			2	
80	14	2031	200			2	
80	17	2466	200			2	
90	3	435	75			2	
90	7	1015	100			2	
90	10	1450	125			2	

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

**TABLE 6** *Continued*

		<b>AA MATERIALS</b>							
<b>Suffix Requirements</b>	Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8	
A13	Heat resistance, Test Method D 573, 70 h at 70°C:								
	Change in hardness, max, points		±15		+10	+10			
	Change in tensile strength, max, %		±30		-25	-25			
	Change in ultimate elongation, max, %		-50		-25	-25			
B13	Compression set, Test Methods D 395, Method B, max, %, 22 h at 70°C			25	25	25			
B33	Compression set, Test Methods D 395, Method B, max, %, 22 h at 70°C			50	50	50			
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %		85	†	85	†			
C20	Resistance to outdoor aging, Test Method D 1171, quality retention rating, min, %		85	85	85	85			
EA14	Water resistance, Test Method D 471, 70 h at 100°C, volume change, max, %		10	10	10	10			
F17	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -40°C		pass	pass	pass	pass			
G21	Tear resistance, Test Method D 624, Die C:								
	under 7.0 MPa tensile strength, min, kN/m			22	22	22			
	over 7.0 MPa tensile strength, min, kN/m			26	26	26			
K11	Adhesion, Test Methods D 429, min:								
	Method A, min, MPa		1.4	2.8	1.4	2.8			
K21	Adhesion, Test Method D 429, Method B, min, MPa		7	7	7	9			
P2	Staining resistance, Test Methods D 925, Method B, control panel		pass	pass	pass	pass			
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.

**TABLE 6** *Continued*

<b>AK MATERIALS</b>							
<b>Basic Requirements</b>							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 70°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 70°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 70°C	Available Suffix Grade Numbers
	MPa	psi					
40	3	435	400	Change in tensile strength, ±30 %			2
50	3	435	400				2
60	5	725	300	Change in ultimate elongation, – 50 % max	Volume change, + 10 % max	Compression set, 50 % max	2
70	7	1015	250				2
80	7	1015	150	Change in durometer hardness, ±15 points			3
90	7	1015	100				3

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1

<b>AK MATERIALS</b>									
<b>Suffix Requirements</b>		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A14	Heat resistance, Test Method D 573, 70 h at 100°C:								
	Change in durometer hardness, max, points		+15	+15					
	Change in tensile strength, max, %		–15	–15					
	Change in ultimate elongation, max, %		–40	–40					
B33	Compression set, Test Methods D 395, Method B, 22 h at 70°C max, %		50	50					
EO14	Fluid resistance, Test Method D 471, Oil No. 1, 70 h at 100°C:								
	Change in tensile strength, max. %		†	†					
	Change in ultimate elongation, max. %		†	†					
	Change in durometer hardness, max, points		†	†					
	Change in volume, max, %		–3 to +5	–3 to +5					
EO34	Fluid resistance, Test Method D 471, Oil No. 3, 70 h at 100°C:								
	Change in durometer hardness, points		–5 to +10	–5 to +10					
	Change in tensile strength, max. %		–30	–30					
	Change in ultimate elongation, max, %		–50	–50					
	Change in volume, max, %		†	†					
F17	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at – 40°C			pass					
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only, no suffix requirements for Grade No. 1.

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.



TABLE 6 Continued

Basic Requirements							BA MATERIALS
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 100°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 100°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 70°C	Available Suffix Grade Numbers
	MPa	psi					
20 <sup>B</sup>	6	870	400				3
30	7	1015	400				2
30	10	1450	400				2, 3, 4, 5
30	14	2031	400				2, 3, 4, 5
40	3	435	300				2, 8
40	7	1015	300				2, 8
40	10	1450	400				2, 3, 4, 5, 6
40	14	2031	400				2, 3, 4, 5
50	7	1015	300				2, 8
50	10	1450	400				2, 3, 4, 5, 6
50	14	2031	400				2, 3, 4, 5
50	17	2466	400				2, 3, 4, 5
60	3	435	250	Change in tensile strength, ±30 %			8
60	6	870	250				8
60	7	1015	300	Change in ultimate elongation, – 50 % max	No requirement	Compression set, 50 % max	2, 8
60	10	1450	350				2, 3, 4, 5, 6
60	14	2031	400	Change in durometer hardness, ±15 points			2, 3, 4, 5, 6
60	17	2466	400				2, 3, 4, 5, 6
70	3	435	150				8
70	6	870	150				8
70	7	1015	200				2, 8
70	8	1160	200				8
70	10	1450	250				2, 3, 4, 5, 6
70	14	2031	300				2, 3, 4, 5
70	17	2466	300				2, 3, 4, 5
80	7	1015	100				2, 7
80	10	1450	150				2, 4
80	14	2031	200				2, 4
90	3	435	75				7
90	7	1015	100				2, 7
90	10	1450	125				2, 4

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

<sup>B</sup>Materials would typically be 20 to 25 durometer based upon current capability.

Suffix Requirements		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A14	Heat resistance, Test Method D 573, 70 h at 100°C: Change in hardness, max, points Change in tensile strength, max, % Change in ultimate elongation, max, %			+10 –25 –25	+10 –25 –25				
B13	Compression set, Test Methods D 395, Method B, max, %, 22 h at 70°C			25			25		25
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %		100	100	100	100	100	100	100
F17	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at – 40°C		pass	pass	pass	pass			
F19	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at – 55°C			pass		pass			
K11	Adhesion, Test Methods D 429, min: Method A, min, MPa			1.4	1.4	1.4	1.4		
K21	Adhesion, Test Methods D 429, min: Method B, min, kN/m			7	7	7			
K31	Adhesion, bond made after vulcanization			<sub>B</sub>	<sub>B</sub>	<sub>B</sub>			
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

<sup>B</sup>Suffix K31 indicates that the material shall be free of surface conditions and compound constituents that are or may become deleterious to cement adhesion.

**TABLE 6** *Continued*

							<b>BC MATERIALS</b>
<b>Basic Requirements</b>							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 100°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 100°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 100°C	Available Suffix Grade Numbers
	MPa	psi					
30	3	435	300				2, 5
30	7	1015	400				2, 5
30	10	1450	500				2, 5
30	14	2031	500				2
40	3	435	300				2
40	7	1015	400				2, 5
40	10	1450	500				2, 5
40	14	2031	500				2, 5
40	17	2466	500				2
50	3	435	300				2, 5
50	7	1015	300				2, 5
50	10	1450	350				2, 5, 6
50	14	2031	400				2, 5, 6
50	17	2466	450				2, 6
50	21	3046	500				2, 6
50	24	3481	500				2, 6
60	3	435	300	Change in tensile strength, ±30 %			3, 5
60	7	1015	300	Change in ultimate elongation, – 50 % max			3, 5
60	10	1450	350	Change in durometer hardness, ±15 points	Volume change, + 120 % max	Compression set, 80 % max	3, 5, 6
60	14	2031	350				3, 6
60	17	2466	400				3, 6
60	21	3046	400				3, 6
60	24	3481	400				3, 6
70	3	435	200				3, 5
70	7	1015	200				3, 5
70	10	1450	250				3, 5, 6
70	14	2031	300				3, 5, 6
70	17	2466	300				3, 6
70	21	3046	300				3, 6
80	3	435	100				4
80	7	1015	100				4
80	10	1450	100				4
80	14	2031	150				4
90	3	435	50				4
90	7	1015	100				4
90	10	1450	150				4
90	14	2031	150				4

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

**TABLE 6** *Continued*

		<b>BC MATERIALS</b>							
<b>Suffix Requirements</b>	Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8	
A14	Heat resistance, Test Method D 573, 70 h at 100°C:								
	Change in hardness, max points	+15	+15	+15	+15	+15			
	Change in tensile strength, max, %	-15	-15	-15	-15	-15			
	Change in ultimate elongation, max, %	-40	-40	-40	-40	-40			
B14	Compression set, Test Methods D 395, Method B, 22 h at 100°C, max, %	35	35	35	35	35			
C12	Resistance to ozone, Test Method D 1171	100	100	100	100	100			
C20	Resistance to outdoor aging, Test Method D 1171, quality retention rating, min, %	†	†	†	†	†			
EO14	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 100°C:								
	Change in hardness, points	±10	±10	±10	±10	±10			
	Change in tensile strength, max, %	-30	-30	-30	-30	-30			
	Change in ultimate elongation, max, %	-30	-30	-30	-30	-30			
	Change in volume, %	-10 to +15	-10 to +15	-10 to +15	-10 to +15	-10 to +15			
EO34	Fluid resistance, Test Method D 471, No. 3 Oil, <sup>B</sup> 70 h at 100°C:								
	Change in tensile strength, max, %	-70	-60	-45	-60	-60			
	Change in ultimate elongation, max, %	-55	-50	-30	-60	-50			
	Change in volume, %	+120	+100	+80	+100	+100			
F17	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -40°C	pass	pass	pass					
F19	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -55°C				pass				
G21	Tear resistance, Test Method D 624, Die C:								
	Under 7.0 MPa tensile load, min, kN/m	22	22	22					
	7.0 to 10 MPa tensile load, min, kN/m	26	26	26					
	10 MPa tensile load and over, min, kN/m	26	26	26	26	26			
K11	Adhesion, Test Methods D 429, min: Method A, min, MPa	1.4	1.4	1.4	1.4	2.8			
P2	Staining resistance, Test Methods D 925, Method B, control panel, nonstaining	†	†	†					
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

<sup>†</sup>The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.

<sup>B</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

**TABLE 6** *Continued*

							<b>BE MATERIALS</b>	
<b>Basic Requirements</b>								
Durometer Hardness, $\pm 5$ Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 100°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 100°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 100°C	Available Suffix Grade Numbers	
	MPa	psi						
40	3	435	500			40	2	
40	7	1015	500			40	2	
50	3	435	350			40	2	
50	6	870	350			40	2	
50	7	1015	400			40	2	
50	10	1450	400			40	2, 3	
50	14	2031	400			40	2	
60	3	435	300			40	2	
60	6	870	300			40	2	
60	7	1015	350			40	2	
60	10	1450	350	Change in tensile strength, $\pm 30$ %		40	2, 3	
60	14	2031	350				40	2
70	3	435	200	Change in ultimate elongation, - 50 % max	Volume change, +80 % max	50	2	
70	6	870	200					50
70	7	1015	200	Change in durometer hardness, $\pm 15$ points		50	2	
70	10	1450	250				50	2, 3
70	14	2031	250				50	2
70	17	2466	250				50	2
80	7	1015	100				50	2
80	10	1450	100			50	2	
80	14	2031	150			50	2	
80	17	2466	150			50	2	
90	7	1015	100			50	2	
90	10	1450	100			50	2	
90	14	2931	150			50	2	

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

**TABLE 6** *Continued*

		<b>BE MATERIALS</b>							
<b>Suffix Requirements</b>	Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8	
A14	Heat resistance, Test Method D 573, 70 h at 100°C:								
		+15	+15						
			-15	-15					
			-40	-40					
B14	Compression set, Test Methods D 395, Method B, max, %, 22 h at 100°C								
		25	25						
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %								
		100	100						
C20	Resistance to outdoor aging, Test Method D 1171								
		†	†						
EO14	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 100°C:								
			±10	±10					
			-30	-30					
			-30	-30					
			-10 to +15	-10 to +15					
EO34	Fluid resistance, Test Method D 471, No. 3 Oil, <sup>B</sup> 70 h at 100°C:								
			-50	-50					
			-40	-40					
F17	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -40°C								
			pass						
F19	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -55°C								
				pass					
G21	Tear resistance, Test Method D 624, Die C: 10 MPa tensile load and over, min, kN/m								
			26						
K11	Adhesion, Test Methods D 429, Method A, min, MPa								
			1.4						
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

<sup>†</sup>The requirement is applicable, and materials are available having those characteristics, but values have not yet been established.

<sup>B</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

**TABLE 6** *Continued*

<b>BF MATERIALS</b>							
<b>Basic Requirements</b>							
Durometer Hardness, $\pm 5$ Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 100°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 100°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 100°C	Available Suffix Grade Numbers
	MPa	psi					
60	3	435	200				2
60	6	870	200				2
60	7	1015	250				2
60	8	1160	250				2
60	10	1450	300				2
60	14	2031	350				2
60	17	2466	350				2
70	3	435	150	Change in tensile strength, $\pm 30$ %			2
70	6	870	150	Change in ultimate elongation, $-50$ % max	Volume change, $+60$ % max	Compression set, $50$ % max	2
70	7	1015	200	Change in durometer hardness, $\pm 15$ points			2
70	8	1160	200				2
70	10	1450	250				2
70	14	2031	250				2
70	17	2466	300				2
80	3	435	100				2
80	7	1015	100				2
80	10	1450	125				2
80	14	2031	125				2

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

<b>BF MATERIALS</b>									
<b>Suffix Requirements</b>		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
B14	Compression set, Test Methods D 395, Method B, max, %, 22 h at 100°C		25						
B34	Compression set, Test Methods D 395, Method B, max, %, 22 h at 100°C		25						
EO14	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 100°C:								
	Change in hardness, points		$\pm 10$						
	Change in tensile strength, max, %		$-25$						
	Change in ultimate elongation, max, %		$-45$						
	Change in volume, %		$-10$ to $+10$						
EO34	Fluid resistance, Test Method D 471, No. 3 Oil, 70 h at 100°C:								
	Change in hardness, max, points		$-20$						
	Change in tensile strength, max, %		$-45$						
	Change in ultimate elongation, max, %		$-45$						
	Change in volume, %		$0$ to $+60$						
F19	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at $-55^\circ\text{C}$		pass						
K11	Adhesion, Test Methods D 429, Method A, MPa			<i>B</i>					
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

<sup>B</sup>Materials are available that can be bonded to metal during vulcanization. Because of the wide variety of compounds in use, combined with manifold end-use requirements, no values are shown. Test Methods D 429 and requirements should be agreed upon by the supplier and user.

TABLE 6 Continued

BG MATERIALS							
Basic Requirements							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 100°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 100°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 100°C	Available Suffix Grade Numbers
	MPa	psi					
40	7	1015	450				2, 5
40	10	1450	450				2, 5
50	3	435	300				2, 5
50	6	870	300				2
50	7	1015	350				2, 5
50	8	1160	350				2
50	10	1450	300				2, 3, 4, 5
50	14	2031	350				2, 3, 4, 5
50	21	3046	400				3, 4
60	3	435	200				2, 5
60	6	870	200				2
60	7	1015	250				2, 5
60	8	1160	250				2
60	10	1450	300				2, 5
60	14	2031	300				2, 3, 4, 5
60	17	2466	350				2
60	21	3046	350	Change in tensile strength, ±30 %			3, 4
60	28	4061	400	Change in ultimate elongation, -50 % max	Volume change, +40 % max	Compression set, 50 % max	3, 4
70	3	435	150	Change in durometer hardness, ±15 points			2, 5
70	6	870	150				2
70	7	1015	200				2, 5
70	8	1160	200				2
70	10	1450	250				2, 5
70	14	2031	250				2, 3, 4, 5
70	17	2466	300				2, 3
70	21	3046	350				3, 4
70	28	4061	400				3, 4
80	3	435	100				6, 7
80	7	1015	100				6, 7
80	10	1450	125				6, 7
80	14	2031	125				3, 4, 6, 7
80	21	3046	300				3, 4
80	28	4061	350				3, 4
90	3	435	50				6, 7
90	7	1015	100				6, 7
90	10	1450	100				6, 7

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

TABLE 6 Continued

		BG MATERIALS							
Suffix Requirements	Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8	
A14	Heat resistance, Test Method D 573, 70 h at 100°C:								
	Change in hardness, max, points			±5	+15	+15			
	Change in tensile strength, max, %			±15	-20	-20			
	Change in ultimate elongation, max, %			-15	-40	-40			
B14	Compression set, Test Methods D 395, Method B, max, %, 22 h at 100°C		25	50	50	25	25	25	
B34	Compression set, Test Methods D 395, Method B, max, %, 22 h at 100°C		25			25	25		
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %			†	†				
C20	Resistance to outdoor aging, Test Method D 1171			†	†				
EA14	Water resistance, Test Method D 471, 70 h at 100°C:								
	Change in hardness, points		±10				±10		
	Change in volume, %		±15				±15		
EF11	Fluid resistance, Test Method D 471, Reference Fuel A, 70 h at 23°C:								
	Change in hardness, points		±10				±10		
	Change in tensile strength, max, %		-25				-25		
	Change in ultimate elongation, max, %		-25				-25		
	Change in volume, %		-5 to +10				-5 to +10		
EF21	Fluid resistance, Test Method D 471, Reference Fuel B, 70 h at 23°C:								
	Change in hardness, points		0 to -30				0 to -30		
	Change in tensile strength, max, %		-60				-60		
	Change in ultimate elongation, max, %		-60				-60		
	Change in volume, %		0 to +40				0 to +40		
EO14	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 100°C:								
	Change in hardness, max, points		-5 to +10	-7 to +5	-7 to +5	-5 to +15	-5 to +15	-5 to +5	
	Change in tensile strength, max, %		-25	-20	-20	-25	-25	-25	
	Change in ultimate elongation, max, %		-45	-40	-40	-45	-45	-45	
	Change in volume, %		-10 to +5	-5 to +10	-5 to +5	-10 to +5	-10 to +5	-10 to +5	
EO34	Fluid resistance, Test Method D 471, No. 3 Oil, 70 h at 100°C:								
	Change in hardness, points		-10 to +5	-10 to +5	-10 to +5	0 to -15	0 to -20	-10 to +5	
	Change in tensile strength, max, %		-45	-35	-35	-45	-45	-45	
	Change in ultimate elongation, max, %		-45	-40	-40	-45	-45	-45	
	Change in volume, %		0 to +25	+16 to +35	0 to +6	0 to +35	0 to +35	0 to +25	
F16	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -35°C							pass	
F17	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -40°C		pass				pass		
F19	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -55°C			pass	pass	pass			
K11	Adhesion, Test Methods D 429, Method A, MPa		B	B	B	B	B	B	
P2	Staining resistance, Test Methods D 925, Method B, control panel			pass	pass				
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

<sup>B</sup>Materials are available that can be bonded to metal during vulcanization. Because of the wide variety of compounds in use, combined with manifold end-use requirements, no values are shown. Test Methods D 429 and requirements should be agreed upon by the supplier and user.

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established. These values should be determined between the end user and producer.



**TABLE 6** *Continued*

<b>BK MATERIALS</b>							
<b>Basic Requirements</b>							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 100°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 100°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 100°C	Available Suffix Grade Numbers
	MPa	psi					
60	3	435	200				4
60	6	870	200				4
60	7	1015	250				4
60	8	1160	250				4
60	10	1450	300				4
60	14	2031	350				4
60	17	2466	350				4
70	3	435	150				4
70	6	870	150	Change in tensile strength, ±30 %	Volume change, + 10 % max	Compression set, 50 % max	4
70	7	1015	200				4
70	8	1160	200	Change in ultimate elongation, - 50 % max			4
70	10	1450	250		4		
70	14	2031	250	Change in durometer hardness, ±15 points			4
70	17	2466	300		4		
80	3	435	100				4
80	7	1015	100				4
80	10	1450	125				4
80	14	2031	125				4
90	3	435	50				4
90	7	1015	100				4
90	10	1450	100				4

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

TABLE 6 Continued

		BK MATERIALS							
Suffix Requirements	Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8	
A24	Heat resistance, Test Method D 865, 70 h at 100°C:								
					±10				
					-20				
					-30				
B14	Compression set, Test Methods D 395, Method B, max, %, 22 h at 100°C								
					25				
B34	Compression set, Test Methods D 395, Method B, max, %, 22 h at 100°C								
					25				
EF11	Fluid resistance, Test Method D 471, Reference Fuel A, 70 h at 23°C:								
					±5				
					-20				
					-20				
					±5				
EF21	Fluid resistance, Test Method D 471, Reference Fuel B, 70 h at 23°C:								
					0 to -20				
					-50				
					-50				
					0 to +25				
EO14	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 100°C:								
					±5				
					-20				
					-20				
					-10 to 0				
EO34	Fluid resistance, Test Method D 471, No. 3 Oil, 70 h at 100°C:								
					-10 to +5				
					-20				
					-30				
					0 to +5				
K11	Adhesion, Test Methods D 429, Method A, MPa								
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

<sup>B</sup>Materials are available that can be bonded to metal during vulcanization. Because of the wide variety of compounds in use, combined with manifold end-use requirements, no values are shown. Test Methods D 429 and requirements should be agreed upon by the supplier and user.

**TABLE 6** *Continued*

							<b>CA MATERIALS</b>
							<b>Basic Requirements</b>
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 125°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 150°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 100°C	Available Suffix Grade Numbers
	MPa	psi					
30	7	1015	500				2
30	10	1450	500				2
40	7	1015	400				2
40	10	1450	400				2
40	14	2031	400				2
50	7	1015	300				3
50	10	1450	300				4
50	14	2031	350				4
50	17	2466	350	Change in tensile strength, ± 30 %			4
60	7	1015	250	Change in ultimate elongation, – 50 % max	No requirements	Compression set, 60 % max	3
60	10	1450	250	Change in durometer hardness, ±15 points			4
60	14	2031	250				4
70	7	1015	200				3
70	10	1450	200				4, 5
70	14	2031	200				4, 5
80	7	1015	150				6
80	10	1450	150				7, 8
80	14	2031	150				7, 8
90	7	1015	100				6
90	10	1450	100				7, 8

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

									<b>CA MATERIALS</b>
<b>Suffix Requirements</b>		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A25	Heat resistance, Test Method D 865, 70 h at 125°C:								
	Change in hardness, max, points		+10	+10	+10	+10	+10	+10	+10
	Change in tensile strength, max, %		–20	–20	–20	–20	–20	–20	–20
	Change in ultimate elongation, max, %		–40	–40	–40	–40	–50	–40	–40
B44	Compression set, Test Methods D 395, Method B, 70 h at 100°C, plied specimen, max, %		35	50					
B35	Compression set, Test Methods D 395, Method B, 22 h at 125°C, plied specimen, max, %		70	70	70	50	70	70	50
C32	Resistance to ozone, Test Method D 1171, exposure Method B		pass	pass	pass	pass	pass	pass	pass
EA14	Water resistance, Test Method D 471, 70 h at 100°C, volume change, %		±5	±5	±5	±5	±5	±5	±5
F17	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at –40°C		pass	pass	pass	pass	pass	pass	pass
F18	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at –50°C		pass	pass	pass	pass		pass	
F19	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at –55°C				pass				
G11	Tear resistance, Test Method D 624, Die B, min, kN/m		17	26	26	26	26	26	26
G21	Tear resistance, Test Method D 624, Die C, min, kN/m		17	26	26	26	26	26	26
K11	Adhesion, Test Methods D 429, Method A, min, MPa			1.4	2.8	2.8	1.4	2.8	2.8
P2	Staining resistance, Test Methods D 925, Method B, control panel		pass	pass	pass	pass	pass	pass	pass
R11	Resilience in compression, Test Methods D 945, min, %		70	50	60				
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

TABLE 6 Continued

Basic Requirements							CE MATERIALS
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 125°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 125°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 70°C	Available Suffix Grade Numbers
	MPa	psi					
50	14	2031	400				2, 3
60	10	1450	350				2, 3
60	14	2031	400				2, 3
60	17	2466	400	Change in tensile strength, ±30 %			2, 3
70	7	1015	200	Change in ultimate elongation, -50 % max	Volume change, +80 % max	Compression set, 80 % max	2, 3
70	10	1450	250				2, 3
70	14	2031	300	Change in durometer hardness, ± 15 points			2, 3
70	17	2466	300				2, 3
80	7	1015	200				2, 3
80	10	1450	250				2, 3
80	14	2031	250				2, 3

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

Suffix Requirements		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A16	Heat resistance, Test Method D 573, 70 h at 150°C:								
	Change in hardness, points			±20					
	Change in tensile strength, %			±30					
	Change in ultimate elongation, max, %			-60					
B15	Compression set, Test Methods D 395, Method B, max, %, 22 h at 125°C		60	80					
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %		†	†					
C20	Resistance to outdoor aging, Test Method D 1171		†	†					
F19	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -55°C		pass	pass					
P2	Staining resistance, Test Methods D 925, Method B, control panel		pass	pass					
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.

TABLE 6 Continued

							CH MATERIALS
Basic Requirements							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 865, 70 h at 125°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 125°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 100°C	Available Suffix Grade Numbers
	MPa	psi					
60	3	435	200				2, 3
60	6	870	200	2, 3			
60	7	1015	250	2, 3			
60	8	1160	250	2, 3			
60	10	1450	300	2, 3, 5, 6			
60	14	2031	350	2, 3			
60	17	2466	350	2, 3			
70	3	435	150	2, 3			
70	6	870	150	Change in tensile strength,			2, 3
70	7	1015	200	±30 %			2, 3
70	8	1160	200	Change in ultimate	Volume change,	Compression set,	2, 3
70	10	1450	250	elongation, -50 % max	+30 % max	50 % max	2, 3
70	14	2031	250	Change in durometer			2, 3, 5, 6
70	17	2466	300	hardness, ± 15 points			2, 3
80	3	435	100	3, 4			
80	7	1015	100	3, 4			
80	10	1450	125	3, 4			
80	14	2031	125	3, 4, 5, 6			
90	3	435	50	3, 4			
90	7	1015	100	3, 4			
90	10	1450	100		3, 4, 5, 6		

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

									CH MATERIALS
Suffix Requirements		Grade	Grade	Grade	Grade	Grade	Grade	Grade	Grade
		1 <sup>A</sup>	2	3	4	5	6	7	8
A25	Heat resistance, Test Method D 865, 70 h 125°C:								
	Change in hardness, points		0 to +15	0 to +15	0 to +15	0 to +10	0 to +10		
	Change in tensile strength, max, %		-25	-25	-25	-10	-20		
	Change in ultimate elongation, max, %		-50	-50	-50	-40	-30		
B14	Compression set, Test Methods D 395, Method B, max, %, 22 h at 100°C		25	25	25	30	25		
B34	Compression set, Test Methods D 395, Method B, max, %, 22 h at 100°C		25	25		30	25		
C12	Resistance to ozone retention rating, Test Method D 1171					100	100		
C20	Resistance to outdoor aging, Test Method D 1171					†	†		
EF31	Fluid resistance, Test Method D 471, Reference Fuel C, 70 h at 23°C:								
	Change in hardness, points		0 to -30		0 to -30	0 to -20	0 to -20		
	Change in tensile strength, max, %		-60		-60	-50	-50		
	Change in ultimate elongation, max, %		-60		-60	-60	-50		
	Change in volume, %		0 to +50		0 to +50	0 to +40	0 to +40		

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.

**TABLE 6** *Continued*

		<b>CH MATERIALS</b>							
<b>Suffix Requirements</b>	Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8	
EO15	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 125°C:								
	Change in hardness, points		0 to +10		0 to +10				
	Change in tensile strength, max, %		-20		-20				
	Change in ultimate elongation, max, %		-35		-35				
	Change in volume, %		-15 to +5		-15 to +5				
EO16	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 150°C:								
	Change in hardness, points			0 to +10					
	Change in tensile strength, max, %			-20					
	Change in ultimate elongation, max, %			-40					
	Change in volume, %			-15 to +5					
EO35	Fluid resistance, Test Method D 471, No. 3 Oil, <sup>B</sup> 70 h at 125°C:								
	Change in hardness, points		±10		±10				
	Change in tensile strength, max, %		-15		-15				
	Change in ultimate elongation, max, %		-30		-30				
	Change in volume, %		0 to +25		0 to +25				
EO36	Fluid resistance, Test Method D 471, No. 3 Oil, <sup>B</sup> 70 h at 150°C:								
	Change in hardness, points			±10		-5 to +10	-5 to +10		
	Change in tensile strength, max, %			-35		-10	-15		
	Change in ultimate elongation, max, %			-35		-50	-40		
	Change in volume, %			0 to +25		0 to +10	0 to +15		
F14	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -18°C					pass			
F16	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -35°C				pass				
F17	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -40°C		pass				pass		
K11	Adhesion, Test Methods D 429, Method A, MPa		C	C	C	C			
Z	(Special requirements) Any requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1

<sup>B</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

<sup>C</sup>Materials are available that can be bonded to metal during vulcanization. Because of the wide variety of compounds in use, combined with manifold end-use requirements, no values are shown. Test Methods D 429 and requirements should be agreed upon by the supplier and user.

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.

**TABLE 6** *Continued*

<b>DA MATERIALS</b>							
<b>Basic Requirements</b>							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 150°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 150°C	Compression Set, Test Methods D 395, Plied, max, %, 22 h at 150°C	Available Suffix Grade Numbers
	MPa	psi					
50	7	1015	300				2
50	10	1450	300				2
50	14	2031	350				2
60	7	1015	250	Change in tensile strength, ±30 % Change in ultimate elongation, – 50 % max Change in durometer hardness, ±15 points	No Requirement	Compression set, 50 % max	2,3
60	10	1450	250				2,3
60	14	2031	300				2,3
70	7	1015	200				2,3
70	10	1450	200				2,3
70	14	2031	200				2,3
80	7	1015	150				2,3
80	10	1450	150				2,3
80	14	2031	150				2,3

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

<b>DA MATERIALS</b>									
<b>Suffix Requirements</b>		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A26	Heat resistance, Test Methods D 865, 70 h at 150°C: Change in hardness, max, points Change in tensile strength, max, % Change in ultimate elongation, max, %		+10 –20 –20	+10 –20					
B36	Compression set, Test Methods D 395, Method B, 22 h at 150°C, plied, max, %		40	25					
C32	Resistance to ozone, Test Method D 1171, Exposure, Method B		pass	pass					
EA14	Water resistance, Test Method D 471, 70 h at 100°C, volume change, %		±5	±5					
F19	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at –55°C		pass	pass					
G11	Tear resistance, Test Method D 624, Die B, min, kN/m		17	17					
G21	Tear resistance, Test Method D 624, Die C, min, kN/m		17	17					
K11	Adhesion, Test Methods D 429, Method A, min, MPa			1.4					
P2	Staining resistance, Test Methods D 925, Method B, control panel		pass	pass					
R11	Resilience in compression, Test Methods D 945, min, %		60	60					
Z	(Special requirements) Any special requirement shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1

TABLE 6 *Continued*

DE MATERIALS							
Basic Requirements							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 150°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 150°C	Compression Set, Test Methods D 395, Method B, Solid, max, %, 22 h at 125°C	Available Suffix Grade Numbers
	MPa	psi					
60	10	1450	350				2
60	14	2031	400				2,3
60	17	2466	400				2,3,4
70	7	1015	200	Change in durometer hardness, ±15 points Change in tensile strength, ±30 % Change in ultimate elongation, -50 % max	Volume change, +80 % max	Compression set, +80 % max	2
70	10	1450	250				5
70	14	2031	300				6
70	17	2466	300				6
80	7	1015	200				2
80	10	1450	200				2
80	14	2031	250				2
90	10	1450	150				5
90	14	2031	150				5

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

DE MATERIALS							
Suffix Requirements		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6
A16	Heat resistance, Test Method D 573, 70 h at 150°C:						
	Change in hardness, points		15	15	15		15
	Change in tensile strength, %		30	30	30		30
	Change in ultimate elongation, max, %		-30	-30	-30		-30
B15	Compression set, Test Methods D 395, Method B, 22 h at 125°C, max, %		55	35	25	35	30
C12	Resistance to ozone, Test Method D 1171		<i>B</i>	<i>B</i>	<i>B</i>	<i>B</i>	<i>B</i>
EO36	Fluid resistance, Test Method D 471, No. 3 Oil, 70 h at 150°C:						
	Volume change, max, %		+70	+70		+60	
F16	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -35°C		pass			pass	
F17	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -40°C			pass	pass		pass
Z	(Special Requirements) Any special requirement shall be specified in detail, including test methods.						

<sup>A</sup>Basic properties only—no-suffix requirements for Grade No. 1.

<sup>B</sup>The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.



TABLE 6 Continued

DF MATERIALS							
Basic Requirements							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 865, 70 h at 150°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 150°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 150°C	Available Suffix Grade Numbers
	MPa	psi					
40	6	870	225			80	2
50	7	1015	225			80	2
60	8	1160	175	Change in tensile strength, ±30 %	Volume change, + 60 % max	80	2
70	6	870	100				
70	8	1160	150	Change in ultimate elongation, -50 % max		90	5
80	6	870	100	Change in durometer hardness, ± 15 points		80	2
80	8	1160	150			90	5
90	7	1015	125			80	3
						85	4

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

DF MATERIALS									
Suffix Requirements		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A26	Heat resistance, Test Method D 865, 70 h at 150°C:								
	Change in hardness, max, points		+10	+10	+10	+10			
	Change in tensile strength, max, %		-25	-25	-25	-25			
	Change in ultimate elongation, max, %		-30	-30	-30	-30			
B16	Compression set, Test Methods D 395, Method B, max, %, 22 h at 150°C		50	60	75	80			
B36	Compression set, Test Methods D 395, Method B, max, %, 22 h at 150°C		75	80	85				
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %		†	†	†	†			
C20	Resistance to weather aging, Test Method D 1171		†	†	†	†			
EO16	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 150°C:								
	Change in hardness, points		-8 to +15	-8 to +10	-8 to +10	-8 to +10			
	Change in tensile strength, max, %		-20	-20	-20	-30			
	Change in ultimate elongation, max, %		-30	-30	-30	-50			
	Change in volume, %		-5 to +10	-5 to +10	-5 to +10	-5 to +10			
EO36	Fluid resistance, Test Method D 471, No. 3 Oil, 70 h at 150°C:								
	Change in hardness, max, points		-30	-30	-30	-30			
	Change in tensile strength, max, %		-60	-60	-60	-60			
	Change in ultimate elongation, max, %		-40	-30	-30	-50			
	Change in volume, %		+50	+50	+50	+50			
F14	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -18°C			pass	pass	pass			
F15	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -25°C		pass						
K11	Adhesion, Test Methods D 429, Method A, min, MPa		1.4	1.4	1.4	1.4			
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.

**TABLE 6** *Continued*

<b>DH MATERIALS</b>							
<b>Basic Requirements</b>							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 865, 70 h at 150°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 150°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 150°C	Available Suffix Grade Numbers
	MPa	psi					
40	7	1015	300			60	2
50	8	1160	250			60	2
60	8	1160	200			60	2
60	9	1450	200	Change in tensile strength, ±30 %		60	2
60	14	2031	250			40	4
70	6	870	100	Change in ultimate elongation, -50 % max	Volume change, +30 % max	75	5
70	8	1160	200				60
70	10	1450	200	Change in durometer hardness, ±15 points		60	3
70	16	2321	250			40	4
80	6	870	100			75	5
80	8	1160	175			60	3
80	10	1450	175			60	3
80	20	2900	150			40	4
90	10	1450	100			60	3
90	20	2900	100			45	

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

<b>DH MATERIALS</b>									
<b>Suffix Requirements</b>		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A26	Heat resistance, Test Method D 865, 70 h at 150°C:								
	Change in hardness, max, points		+10	+10	+10	+10			
	Change in tensile strength, max, %		-25	-25	-15	-25			
	Change in ultimate elongation, max, %		-30	-30	-25	-30			
B16	Compression set, Test Methods D 395, Method B, max, %, 22 h at 150°C		30	30		60			
B36	Compression set, Test Methods D 395, Method B, max, %, 22 h at 150°C		50	50	35				
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %		†	†	†	†			
C20	Resistance to outdoor aging, Test Method D 1171		†	†	†	†			
EO16	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 150°C:								
	Change in hardness, points		-5 to +10	-5 to +10	-5 to +10	-5 to +10			
	Change in tensile strength, max, %		-20	-20	-20	-20			
	Change in ultimate elongation, max, %		-30	-30	-30	-40			
	Change in volume, %		±5	±5	-10 to +5	±5			
EO36	Fluid resistance, Test Method D 471, No. 3 Oil, 70 h at 150°C:								
	Change in hardness, max, points		-15	-15	-15	-15			
	Change in tensile strength, max, %		-40	-30	-40	-40			
	Change in ultimate elongation, max, %		-40	-30	-30	-40			
	Change in volume, %		+25	+25	+25	+25			
F13	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -10°C			pass		pass			
F14	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -18°C		pass						
F17	Low-temperature resistance, Test Method D 2137, Method A, 9.3.2, nonbrittle after 3 min at -40°C				pass				
K11	Adhesion, Test Methods D 429, Method A, bonded during vulcanization, min, MPa		1.4	1.4		1.4			
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.

**TABLE 6** *Continued*

Basic Requirements							EE MATERIALS
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 865, 70 h at 175°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>4</sup> 70 h at 150°C	Compression Set, Test Methods D 395, Method B, Solid, max, %, 22 h at 150°C	Available Suffix Grade Numbers
	MPa	psi					
50	8	1160	400				3
50	10	1450	500				3
50	12	1740	500				
50	14	2031	500				
60	6	870	200				4
60	8	1160	300				3,4,5
60	12	1740	300				3
60	14	2031	400	Change in durometer hardness, ±15 points			3
70	8	1160	200	Change in tensile strength, ±30 %	Volume change, +80 % max	Compression set, 75 % max	3,4,5
70	10	1450	200				4
70	12	1740	300	Change in ultimate elongation, -50 % max			3
80	10	1450	200				4
80	12	1740	200				3,4
80	14	2031	200				3,4,5
80	16	2320	200				3
90	6	870	100				4
90	10	1450	100				3
90	14	2031	100				

<sup>4</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

Suffix Requirements		Grade 1	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A47	Heat resistance, Test Method D 573, 168 h at 175°C:								
	Change in hardness, max, points	Basic requirements only		+10	+20	+10			
	Change in tensile strength, max, %	Basic requirements only		-30	-30	-30			
	Change in ultimate elongation, max, %	Basic requirements only		-50	-65	-50			
B46	Compression set, Test Methods D 395, Method B, plied, 70 h at 150°C, max, %	Basic requirements only		50	75	50			
B37	Compression set, Test Methods D 395, Method B, plied, 22 h at 175°C, max, %	Basic requirements only		50	75	50			
EO16	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 150°C:								
	Change in hardness, max, points	Basic requirements only		-10 to +5	-10 to +5	-10 to +5			
	Change in tensile strength, max, %	Basic requirements only		-25	-25	-25			
	Change in ultimate elongation, max, %	Basic requirements only		-35	-35	-35			
	Change in volume, %	Basic requirements only		±15	±10	±10			
EO36	Fluid resistance, Test Method D 471, No. 3 Oil, <sup>4</sup> 70 h at 150°C:								
	Change in tensile strength, max, %	Basic requirements only		-60	-50	-50			
	Change in ultimate elongation, max, %	Basic requirements only		-55	-50	-50			
	Change in volume, max, %	Basic requirements only		+70	+60	+50			
EA14	Water resistance, Test Method D 471, 70 h at 100°C:								
	Change in volume, max, %	Basic requirements only		+15	+15	+15			
F17	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -40°C	Basic requirements only		pass	pass	pass			
G21	Tear resistance, Test Method D 624, Die C, min, kN/M	Basic requirements only		20	20				

<sup>4</sup>Change in Hardness values are omitted because the round robin data did not support them statistically.

**TABLE 6** *Continued*

<b>EH MATERIALS</b>							
<b>Basic Requirements</b>							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, ASTM D 865, 70 h at 175°C	Oil Immersion, ASTM D 471, No. 3 Oil, <sup>A</sup> 70 h at 150°C	Compression Set, ASTM D 395, Solid, max, %, 22 h at 150°C	Available Suffix Grade Numbers
	MPa	psi					
40	7	1015	250			75	3
50	8	1160	175			75	3
60	6	870	100	Change in durometer hardness, ± 15 points Change in tensile strength, ±30 %	Volume change, ±30 %	75	3
60	9	1306	150			75	3
70	6	870	100	Change in ultimate elongation, -50 % max		75	3
70	9	1306	125		75	3	
80	7	1015	100			75	3

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM 903 oil. See 4.4.1.

<b>EH MATERIALS</b>									
<b>Suffix Requirements</b>		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A27	Heat resistance, Test Method D 865, 70 h at 175°C:								
	Change in hardness, max, points			+10					
	Change in tensile strength, max, %			-30					
	Change in ultimate elongation, max, %			-40					
B17	Compression set, ASTM D 395, Method B, 22 h at 175°C, solid max, %			60					
B37	Compression set, ASTM D 395, Method B, 22 h at 175°C, plied, max, %			60					
E016	Fluid resistance, ASTM D 471, No. 1 Oil, 70 h at 150°C:								
	Change in hardness, points			±5					
	Change in tensile strength, max, %			-20					
	Change in ultimate elongation, max, %			-30					
	Change in volume, %			±5					
EO36	Fluid resistance, ASTM D 471, No.3 Oil, <sup>B</sup> 70 h at 150°C:								
	Change in hardness, points			-20					
	Change in tensile strength, max, %			-40					
	Change in ultimate elongation, max, %			-30					
	Change in volume, %			+25					
F14	Low-temperature resistance, ASTM D 2137, Method A, Pass, °C			pass					
F25	Low-temperature resistance, ASTM D 1053, T100, Pass, °C			pass					
K11	Adhesion, ASTM D 429, Method A, min, MPa			1.4					
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1

<sup>B</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM 903 oil. See 4.4.1.

**TABLE 6** *Continued*

							<b>EK MATERIALS</b>
<b>Basic Requirements</b>							
Durometer Hardness, $\pm 5$ Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, ASTM D 573, 70 h at 150°C	Oil Immersion, ASTM D 471, No. 3 Oil, <sup>A</sup> 70 h at 150°C	Compression Set, ASTM D 395, Solid, max, %, 22 h at 150°C	Available Suffix Grade Numbers
	MPa	psi					
50	9	1305	125	Change in durometer hardness, $\pm 15$ points		60	2
70	10	1450	125	Change in tensile strength, $\pm 30$ %	Volume change, $\pm 10$ % max	60	2
80	10	1450	100	Change in ultimate elongation, $-50$ % max		60	2

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM 903 oil. See 4.4.1.

<b>EK MATERIALS</b>									
<b>Suffix Requirements</b>		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A17	Heat resistance, ASTM D 573, 70 h at 175°C:								
	Change in hardness, points		$\pm 10$						
	Change in tensile strength, %		-25						
	Change in ultimate elongation, max, %		-20 to +30						
A18	Heat aging resistance, ASTM D 573, 70 h at 200°C:								
	Change in hardness, points		-15 to +10						
	Change in tensile strength, max, %		-60						
	Change in ultimate elongation, %		-10 to +40						
B17	Compression set, ASTM D 395, Method B, solid, 22 h at 175°C, max, %		60						
B26	Compression set, ASTM D 395, Method B, solid, 70 h at 150°C, max %		50						
C32	Resistance to ozone, ASTM D 1171, Method B		pass						
EA14	Fluid resistance to ASTM D 471, water, 70 g at 100°C								
	Change in hardness, points		-5 to +10						
	Change in volume		0 to +20						
EF31	Fluid resistance, ASTM D 471, Reference Fuel C, 70 h at room temperature								
	Change in hardness, points		-20 to +5						
	Change in tensile strength, max, %		-50						
	Change in ultimate elongation, max, %		-50						
	Change in volume, max, %		+40						
EO16	Fluid resistance, ASTM D 471, No. 1 Oil, 70 h at 150°C:								
	Change in hardness, points		-10 to +5						
	Change in tensile strength, max, %		-10						
	Change in ultimate elongation, max, %		-20						
	Change in volume, max %		+10						
E036	Fluid resistance, ASTM D 471, No. 3 Oil, <sup>B</sup> 70 h at 150°C:								
	Change in hardness, points		-15 to 0						
	Change in tensile strength, max, %		-20						
	Change in ultimate elongation, max, %		-20						
	Change in volume, max, %		+10						
F19	Low-temperature resistance, ASTM D 2137, Method A, 9.3.2, nonbrittle after 3 min at -55°C		pass						
F49	Low-temperature resistance, ASTM D 1329, after 10 min at -55°C, 10 % retraction, min		pass						

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

<sup>B</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM 903 oil. See 4.4.1.

**TABLE 6** *Continued*

<b>FC MATERIALS</b>							
<b>Basic Requirements</b>							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 200°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 150°C	Compression Set, Test Methods D 395, Plyed, max, %, 22 h at 175°C	Available Suffix Grade Numbers
	MPa	psi					
30	3	435	350			60	2
30	5	725	400			60	2
40	7	1015	400	Change in tensile strength, ±30 %		60	3
50	7	1015	400	Change in ultimate elongation, – 50 % max	Volume change, +120 % max	60	3
50	8	1160	500			80	4
60	7	1015	300	Change in durometer hardness, ±15 points		60	3
60	8	1160	400		80	4	
70	7	1015	200			60	3

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

<b>FC MATERIALS</b>									
<b>Suffix Requirements</b>		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A19	Heat resistance, Test Method D 573, 70 h at 225°C:								
	Change in hardness, max, points		+10	+10	+15				
	Change in tensile strength, max, %		–40	–40	–50				
	Change in ultimate elongation, max, %		–40	–40	–50				
B37	Compression set, Test Methods D 395, Method B, max, %, 22 h at 175°C		40	45	60				
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %		†	†	†				
C20	Resistance to outdoor aging, Test Method D 1171		†	†	†				
EA14	Water resistance, Test Method D 471, 70 h at 100°C:								
	Change in hardness, points		±5	±5	±5				
	Change in volume, %		±5	±5	±5				
EO16	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 150°C:								
	Change in hardness, points		0 to –10	0 to –15	0 to –15				
	Change in tensile strength, max, %		–50	–50	–50				
	Change in ultimate elongation, max, %		–30	–50	–50				
	Change in volume, %		0 to +20	0 to +20	0 to +20				
F1-11	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at – 75°C		pass	pass	pass				
G11	Tear resistance, Test Method D 624, Die B:								
	Under 7.0 MPa load, min, kN/m		5						
	7.0 to 10.5 MPa load, min, kN/m			17	26				
Z	(Special requirements) Any special requirement shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.

TABLE 6 Continued

FE MATERIALS							
Basic Requirements							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 200°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 150°C	Compression Set, Test Methods D 395, Solid, max, %, 22 h at 175°C	Available Suffix Grade Numbers
	MPa	psi					
30	3	435	400	Change in tensile strength, ±30 % Change in ultimate elongation, -50 % max Change in durometer hardness, ±15 points	Volume change, +80 % max	60	2
30	7	1015	500			60	5
40	8	1160	500			60	3
50	8	1160	500			80	4

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

FE MATERIALS						
Suffix Requirements		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5
A19	Heat resistance, Test Method D 573, 70 h at 225°C:					
	Change in hardness, max, points		+10	+10	+15	±10
	Change in tensile strength, max, %		-60	-40	-40	-50
	Change in ultimate elongation, max, %		-60	-60	-60	-50
B37	Compression set, Test Methods D 395, Method B, max, %, 22 h at 175°C		45	50	65	35
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %		†	†	†	
C20	Resistance to outdoor aging, Test Method D 1171		†	†	†	
EA14	Water resistance, Test Method D 471, 70 h at 100°C:					
	Change in hardness, points		±5	±5	±5	±5
	Change in volume, %		±5	±5	±5	±5
EO16	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 150°C:					
	Change in hardness, points		0 to -10	0 to -10	0 to -10	0 to -10
	Change in tensile strength, max, %		-50	-50	-50	-40
	Change in ultimate elongation, max, %		-50	-50	-50	-40
	Change in volume, %		0 to +20	0 to +20	0 to +20	0 to +20
EO36	Fluid resistance, Test Method D 471 No. 3 Oil, 70 h at 150°C:					
	Change in hardness, max, points			†	-40	
	Change in volume, %			+ 80	+80	+65
F19	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -55°C		pass	pass	pass	
G11	Tear resistance, Test Method D 624, Die B:					
	Under 7.0 MPa load, min, kN/m		9			
	7.0 to 10.5 MPa load, min, kN/m			22	26	25
K11	Adhesion, Test Methods D 429, Method A		†	†	†	
K21	Adhesion, Test Methods D 429, Method B		†	†	†	
K31	Bond after vulcanization		<sub>B</sub>	<sub>B</sub>	<sub>B</sub>	<sub>B</sub>
P2	Staining resistance, Test Methods D 925, Method B, control panel		pass	pass	pass	
Z	(Special requirements) Any special requirement shall be specified in detail, including test methods.					

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

<sup>B</sup>Suffix K31 indicates that the materials shall be free of surface conditions and compound constituents that are or may become deleterious to cement adhesion.

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.

**TABLE 6** *Continued*

							<b>FK MATERIALS</b>
<b>Basic Requirements</b>							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 200°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 150°C	Compression Set, Test Methods D 395, Plie <sup>d</sup> , max, %, 22 h at 175°C	Available Suffix Grade Numbers
	MPa	psi					
60	6	870	150	Change in tensile strength, ±30 %		50	2
				Change in ultimate elongation, -50 % max	Volume change, +10 % max		
				Change in durometer hardness, ±15 points			

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

		<b>FK MATERIALS</b>							
<b>Suffix Requirements</b>		Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A19	Heat resistance, Test Method D 573, 70 h at 225°C:								
	Change in hardness, max, points		+15						
	Change in tensile strength, max, %		-45						
	Change in ultimate elongation, max, %		-45						
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %		†						
C20	Resistance to outdoor aging, Test Method D 1171		†						
EF31	Fluid resistance, Test Method D 471, Reference Fuel C, 70 h at 23°C:								
	Change in hardness, points		0 to -15						
	Change in tensile strength, max, %		-60						
	Change in ultimate elongation, max, %		-50						
	Change in volume, %		0 to +25						
EO36	Fluid resistance, Test Method D 471, No. 3 Oil, <sup>B</sup> 70 h at 150°C:								
	Change in hardness, points		0 to -10						
	Change in tensile strength, max, %		-35						
	Change in ultimate elongation, max, %		-30						
	Change in volume, %		0 to +10						
F19	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -55°C		pass						
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.								

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.

<sup>B</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.



**TABLE 6** *Continued*

							<b>GE MATERIALS</b>
<b>Basic Requirements</b>							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 225°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>4</sup> 70 h at 150°C	Compression Set, Test Methods D 395, Plied, max, %, 22 h at 175°C	Available Suffix Grade Numbers
	MPa	psi					
30	3	435	300			50	2
30	5	725	400			50	2
30	6	870	400			50	8
40	3	435	200			50	2
40	5	725	300			50	2
40	6	870	300			50	8
50	3	435	200			50	3
50	5	725	250	Change in tensile strength, ±30 %	Volume change, +80 % max	70	4, 5
50	6	870	250			50	5
50	8	1160	400	Change in ultimate elonga- tion, -50 % max		60	9
60	3	435	100			50	3
60	5	725	200	Change in durometer hard- ness, ± 15 points	70	4, 5	
60	6	870	200		50	5	
70	3	435	60			50	6
70	5	725	150			50	7
70	6	870	150			50	5
80	3	435	50			50	6
80	5	725	150			50	7
80	6	870	100			50	5

<sup>4</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

TABLE 6 Continued

		GE MATERIALS								
Suffix Requirements	Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8	Grade 9	
A19	Heat resistance, Test Method D 573, 70 h at 225°C:									
	Change in hardness, max, points	+10	+10	+10	+10	+10	+10	+10	+10	
	Change in tensile strength, max, %	-25	-25	-30	-25	-25	-25	-25	-30	
	Change in ultimate elongation, max, %	-30	-30	-30	-30	-30	-30	-25	-30	
B37	Compression set, Test Methods D 395, Method B, max, %, 22 h at 175°C	25	30	50	25	30	30	25	40	
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %	†	†	†	†	†	†	†	†	
C20	Resistance to outdoor aging, Test Method D 1171	†	†	†	†	†	†	†	†	
EA14	Water resistance, Test Method D 471, 70 h at 100°C:									
	Change in hardness, points	±5	±5	±5	±5	±5	±5	±5	±5	
	Change in volume, %	±5	±5	±5	±5	±5	±5	±5	±5	
EO16	Fluid resistance, Test Method D 471, No. 1 Oil, 70 h at 150°C:									
	Change in hardness, points	0 to -10	0 to -15	0 to -15	0 to -15	0 to -15	0 to -15	0 to -10	0 to -10	
	Change in tensile strength, max, %	-30	-20	-20	-20	-20	-20	-30	-30	
	Change in ultimate elongation, max, %	-30	-20	-20	-20	-20	-20	-20	-30	
	Change in volume, %	0 to +15	0 to +10	0 to +15	0 to +10	0 to +10	0 to +15	0 to +15	0 to +10	
EO36	Fluid Resistance, Test Method D 471, No. 3 Oil, <sup>B</sup> 70 h at 150°C:									
	Change in hardness, max, points		-30	-35	-30	-40	-40	†	-30	
	Change in volume, %	+60	+60	+60	+60	+60	+60	+60	+60	
F19	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -55°C	pass	pass	pass	pass	pass	pass	pass	pass	
G11	Tear resistance, Test Method D 624, Die B: Under 7.0 MPa load, min, kN/m	5	6	9	9	5	9	9		
	7.0 to 10.5 MPa load, min, kN/m								25	
K11	Adhesion, Test Method D 429, Methods A	†	†	†	†	†	†	†	†	
K21	Adhesion, Test Method D 429, Methods B	†	†	†	†	†	†	†	†	
K31	Bond after vulcanization	c	c	c	c	c	c	c	c	
P2	Staining resistance, Test Methods D 925, Method B, control panel	pass	pass	pass	pass	pass	pass	pass	pass	
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.									

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

<sup>B</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

† The requirement is applicable, and materials are available having these characteristics, but values have not yet been established.

<sup>C</sup>Suffix K31 indicates that the materials shall be free of surface conditions and compound constituents that are or may become deleterious to cement adhesion.

**TABLE 6** *Continued*

<b>HK MATERIALS</b>							
<b>Basic Requirements</b>							
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 250°C	Oil Immersion, Test Method D 471, No. 3 Oil, <sup>A</sup> 70 h at 150°C	Compression Set, Test Methods D 395, Plied, max, %, 22 h at 175°C	Available Suffix Grade Numbers
	MPa	psi					
60	7	1015	200				2, 4, 6
60	10	1450	200				2, 4, 6
60	14	2031	200				2, 4, 6
70	7	1015	175				2, 4, 6
70	10	1450	175	Change in durometer hard- ness, ±15 points			2, 4, 6
70	14	2031	175		Change in tensile strength, ±30 %	Volume change, +10 % max	Compression set, 35 % max
80	7	1015	150	Change in ultimate elonga- tion, -50 % max			2, 4, 6
80	10	1450	150		2, 4, 6		
80	14	2031	150		2, 4, 6		
90	7	1015	100				3, 5, 7
90	10	1450	100				3, 5, 7
90	14	2031	100				3, 5, 7

<sup>A</sup>ASTM Oil No. 3 is no longer commercially available. It has been replaced by IRM903 oil. See 4.4.1.

**TABLE 6** *Continued*

		HK MATERIALS						
Suffix Requirements	Grade 1 <sup>A</sup>	Grade 2	Grade 3	Grade 4	Grade 5	Grade 6	Grade 7	Grade 8
A1-10	Heat resistance, Test Method D 573, 70 h at 250°C:							
	Change in hardness, max, points		+10	+10		+10	+10	
	Change in tensile strength, max, %		-25	-25		-25	-25	
	Change in ultimate elongation, max, %		-25	-25		-25	-25	
A1-11	Heat resistance, Test Method D 573, 70 h at 275°C:							
	Change in hardness, max, points				+10	+10	-5 to +10	-5 to +10
	Change in tensile strength, max, %				-40	-40	-40	-40
	Change in ultimate elongation, max, %				-20	-20	-20	-20
B31	Compression set, Test Methods D 395, Method B, 22 h at 23°C					15	20	
B37	Compression, set, Test Methods D 395, Method B, max, %, 22 h at 175°C		50	30				
B38	Compression set, Test Methods D 395, Method B, max, %, 22 h at 200°C		50	50	50	50	15	20
C12	Resistance to ozone, Test Method D 1171, quality retention rating, min, %		no cracks	no cracks	no cracks	no cracks	no cracks	no cracks
C20	Resistance to outdoor aging, Test Method D 1171		no cracks	no cracks	no cracks	no cracks	no cracks	no cracks
EF31	Fluid resistance, Test Method D 471, Reference Fuel C, 70 h at 23°C:							
	Change in hardness, points		±5	±5	±5	±5	±5	±5
	Change in tensile strength, max, %		-25	-25	-25	-25	-25	-25
	Change in ultimate elongation, max, %		-20	-20	-20	-20	-20	-20
	Change in volume, %		0 to +10	0 to +10	0 to +10	0 to +10	0 to +10	0 to +10
EO78	Fluid resistance, Test Method D 471, Service Liquid <sup>B</sup> No. 101, 70 h at 200°C:							
	Change in hardness, points		-15 to +5	-15 to +5	-15 to +5	-15 to +5		
	Change in tensile strength, max, %		-40	-40	-40	-40		
	Change in ultimate elongation, max, %		-20	-20	-20	-20		
	Change in volume, %		0 to +15	0 to +15	0 to +15	0 to +15		
EO88	Fluid resistance, Test Method D 471 SAE Fluid No. 2, Blend 7700 <sup>C</sup> 70 h at 200°C:							
	Change in hardness, points					-15 to +5	-15 to +5	
	Change in tensile strength, max, %					-40	-40	
	Change in ultimate elongation, max, %					-20	-20	
	Change in volume, %					+25	+25	
F15	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -25°C		pass			pass	pass	
F17	Low-temperature resistance, Test Methods D 2137, Method A, 9.3.2, nonbrittle after 3 min at -40°C				pass			
Z	(Special requirements) Any special requirements shall be specified in detail, including test methods.							

<sup>A</sup>Basic properties only—no suffix requirements for Grade No. 1.

<sup>B</sup>Service Liquid No. 101—di-2 ethyl hexyl sebacate, 99.5 mass %; phenothiazine, 0.5 mass %

<sup>C</sup>SAE Fluid No. 2, Blend 7700 is available from AKZO Nobel Chemicals, Inc. 5 Livingstone Avenue, Debbs Ferry, NY 10522, 1-800-666-1200.

**TABLE 6** *Continued*

<b>Basic Requirements</b>					<b>KK MATERIALS<sup>A</sup></b>	
Durometer Hardness, ±5 Points	Tensile Strength, min		Ultimate Elongation, min, %	Heat Aged, Test Method D 573, 70 h at 300°C	Oil Immersion, Test Method D 471, IRM 903 Oil, 70 h at 150°C	Compression Set, Test Methods D 395, Method B, Plies max, %, 22 h at 200°C
	MPa	psi				
80	11	1595	125	Change in durometer hardness, ±15 points Change in tensile strength, ±30% Change in ultimate elongation, -50% max	Volume change, (+ 10 % max)	Compression set, 25 % max

<sup>A</sup>Supporting data are available from ASTM headquarters. Request RR: D11-1090.

## ANNEX

### (Mandatory Information)

#### A1. Statement of Understanding between SAE CARS and ASTM D11.30

A1.1 The SAE Committee on Automotive Rubber Specifications, (CARS), and the ASTM D11.30 committee affirm that we will work together to maintain the SAE J200 and ASTM D 2000 specification systems. It is our goal to keep the tables in these two documents equivalent. As such, the SAE CARS will be the gatekeeper of any changes and additions to the tables in these specification systems. They will consider, as necessary, the expansion of current tables or the addition of

new tables based on new rubber materials that will better serve both the rubber industry and their customers. SAE CARS may ask for assistance from ASTM D11.30 to provide the necessary laboratories for performing the required interlaboratory testing. In the unlikely event that SAE CARS declines to make any additions or changes to the tables, then ASTM D11.30 may choose to proceed with making those changes or additions if they deem them as additive for the rubber industry.

## APPENDIX

### (Nonmandatory Information)

#### X1. TYPE AND CLASS OF POLYMER USAGE

X1.1 This appendix is intended to assist the users of Classification System D 2000-SAE J200 and is not to be considered as part of the system. Table X1.1 lists the Classification System D 2000-SAE J200 material designations (type

and class) and the type of polymer most often used in meeting the material requirements (type and class). This table is not intended to be limiting; other polymers may be used to meet the same specification.

**TABLE X1.1 Polymers Most Often Used in Meeting  
Material Requirements**

Classification System D2000- SAE J200 Material Designation (Type and Class)	Type of Polymer Most Often Used <sup>4</sup>
AA	Natural rubber, reclaimed rubber, SBR, butyl, EP polybutadiene, polyisoprene
AK	Polysulfides
BA	Ethylene propylene, high-temperature SBR and butyl compounds
BC	Chloroprene polymers (neoprene), cm
BE	Chloroprene polymers (neoprene), cm
BF	NBR polymers
BG	NBR polymers, urethanes
BK	NBR
CA	Ethylene propylene
CE	Chlorosulfonated polyethylene (Hypalon), cm
CH	NBR polymers, epichlorohydrin polymers
DA	Ethylene propylene polymers
DE	CM, CSM
DF	Polyacrylic (butyl-acrylate type)
DH	Polyacrylic polymers, HNBR
EE	AEM
EH	ACM
EK	FZ
FC	Silicones (high strength)
FE	Silicones
FK	Fluorinated silicones
GE	Silicones
HK	Fluorinated elastomers (Viton, Fluorel, etc.)
KK	Perfluoroelastomers

<sup>4</sup> Refer to Practice D 1418.

*The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).*